



HAL
open science

An archaeological and archaeometrical approach of ferrous semi-product : a diachronic qualitative typology (VIIth c. BC. - IIInd c. A.D.)

Philippe Fluzin, Marion Berranger, Sylvain Bauvais, Gaspard Pagès, Philippe
Dillmann

► To cite this version:

Philippe Fluzin, Marion Berranger, Sylvain Bauvais, Gaspard Pagès, Philippe Dillmann. An archaeological and archaeometrical approach of ferrous semi-product : a diachronic qualitative typology (VIIth c. BC. - IIInd c. A.D.). C. CUCINI. Acta mineraria et metallurgica, Studi in onore di Marco Tizzoni, Bergame, Comune di Bergamo/Museo Archeologico, pp.195-204, 2012, Notizie Archeologiche Bergomensi, n°20. halshs-00870717

HAL Id: halshs-00870717

<https://shs.hal.science/halshs-00870717v1>

Submitted on 20 Nov 2016

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

**NOTIZIE
ARCHEOLOGICHE
BERGOMENSI**

$\frac{20}{2012}$

ACTA MINERARIA ET METALLURGICA
Studi in onore di Marco Tizzoni

a cura di
COSTANZA CUCINI



Comune di Bergamo

ISSN: 1127-2155

Periodico di Archeologia del Civico Museo Archeologico di Bergamo
fondato da Stefania Casini

Tutti i diritti riservati
Comune di Bergamo, Museo Archeologico

La responsabilità di quanto riportato nel testo, nonché di eventuali errori e omissioni,
rimane esclusivamente degli Autori.

Autorizzazione del Tribunale di Bergamo, n. 32 del 27.11.1993

Direttore responsabile: Stefania Casini

Segreteria di redazione: Cristina Longhi

Sede: Civico Museo Archeologico di Bergamo, piazza Cittadella 9, 24129 Bergamo

Proprietà: Comune di Bergamo

Stampato da: Grafo s.r.l., Palazzago, Bergamo - novembre 2012

SOMMARIO

Marco Tizzoni <i>Maila Chiaravalle - Chiara Rota</i>	p. 7
À Marco fragments de souvenirs 1990-2010 <i>Michel Mangin avec la collaboration de Maryse Mangin</i>	» 17
MINIERE E METALLURGIA: STUDI REGIONALI	
Attività mineraria e metallurgica nell'Italia centrale durante l'età del rame <i>Daniela Cocchi Genik</i>	» 27
Venti anni di ricerche archeometallurgiche in Italia del nord <i>Costanza Cucini</i>	» 39
La sidérurgie ancienne dans la région de Franche-Comté: trente années de recherches pluridisciplinaires sur la réduction directe dans l'Est de la France (1981-2011) <i>Hervé Laurent - Sylvie Laurent Corsini - Michel Mangin</i>	» 57
Vingt années de recherches sur la sidérurgie ancienne dans le Jura: les vestiges de l'Âge du Fer et de l'Époque romaine <i>Ludwig Eschenlohr</i>	» 79
The production of <i>ferrum Noricum</i> . Largescale Roman iron production in Hüttenberg (Austria) <i>Brigitte Cech</i>	» 91
The role of Celts in popularising iron smelting in the Polish territories <i>Szymon Orzechowski</i>	» 107
Characterising vegetation changes in former mining and metalworking areas during prehistoric and Roman times <i>Tim Mighall - Simon Timberlake - Frank M. Chambers - William O'Brien</i>	» 117
Les Pyrénées, terre d'élection de la réduction directe du minerai de fer (XVII ^e -XIX ^e siècles)? <i>Jean Cantelaube</i>	» 131
L'exploitation et la réduction du fer à haute altitude dans les Alpes du Sud-Ouest: Massifs du Mercantour et de l'Ubaye (Alpes-Maritimes, Alpes-de-Haute-Provence, France) <i>Patrick Rosenthal - Denis Morin</i>	» 159
ARCHEOMETALLURGIA: CONTESTI E ANALISI	
Riflessioni sulla metallurgia fenicia dell'argento nella Penisola Iberica <i>Martina Renzi - Salvador Kovira-Llorens - Ignacio Montero Ruiz</i>	» 185
An archaeological and archaeometrical approach of ferrous semi-product: typology, quality and circulation <i>Philippe Fluzin - Marion Berranger - Sylvain Bauvais - Gaspard Pagès - Philippe Dillmann</i>	» 195

Un'officina di bronzista e la produzione di ottone e di specchi
a *Mediolanum* nel I-II secolo d.C.
Anna Ceresa Mori - Costanza Cucini » 205

La riduzione del rame in Val Lanterna (Sondrio) nella prima età del Ferro:
studio petrografico delle scorie silicatiche
Costanza Cucini - Bruno Messiga- Gisella Rebay - Maria Pia Riccardi » 225

ARCHEOLOGIA, STORIA E ARTE

Le figure di armi della roccia 23 di Foppe di Nadro (Valcamonica):
elementi per la cronologia delle incisioni dell'età del Bronzo
Stefania Casini » 243

Note sulla gestione politica della produzione mineraria
dell'Italia settentrionale (secoli XII-XIV)
Patrizia Mainoni » 255

L'uso della polvere da sparo nelle miniere lombarde d'età moderna
(con un documento)
Raffaello Vergani » 265

In viaggio da Londra a Glasgow
Alba Osimo » 271

Altoforni, castelli e miniere nell'*Orfeo e Euridice* di Tiziano
Orietta Pinessi » 277

An archaeological and archaeometrical approach of ferrous semi-product: typology, quality and circulation

Philippe Fluzin - Marion Berranger - Sylvain Bauvais - Gaspard Pagès - Philippe Dillmann

Introduction

From the raw bloom to the final product, depending on the nature of the latter, several semi-products can be obtained along the *chaîne opératoire*. Some of them are directly transformed on the ironmaking site. Some other, on the contrary are marketed between several workshops, production centres or markets. On relation with the quantity of work to obtain them, or with the quality of the constituting material, they could have different values. For these reasons, understanding the way these semi-products were obtained and in which technico-economical context, but also the way they were comprehended by the ancient craftsmen and blacksmith is a fundamental aspect of ironmaking technical and economical history, whatever the period under interest is. The aim of the general overview presented here is to review, from the archaeological site to the laboratory, the different clues that allow to enlighten several aspects linked to the semi-product production and exchanges. Indeed, even if the archaeometric observations are scientific facts, they can never be considerate out of any archaeological and historical context. Thus, a constant come and go must be undertaken between the physico-chemical data and this context. For example, as far as the metal quality is concerned, added to the fact that numerous parameters will influence the mechanical behaviour of the material, it is important to know that it is not the only aspect that will determine the use of a given material. It is merely a more complex conjunction of its quality, the skill of the blacksmith, the availability of the metals in the technico-economical context under study, etc.

Depending on the place in the *chaîne opératoire*, semi products can be more or less elaborated and of different natures: bloom slightly hammered after a first compaction treatment, ingot obtained after a more important hammering and cleansing, currency and socket bars, with a thinner shape closer to the form of the final artefact, etc.¹.

Semi-products can question several aspects of archaeological and historical studies. At the archaeological site level, it is of great interest to understand the spatial and technical organisation of the site, and sometimes of different production sites in the same area and period. It is also important to evaluate the nature of the forging sequences, the type of activities and production and the quantities. Another crucial question is the nature of the metal that is produced and marketed, linked to his mechanical behaviour, and the value it has in the different technico-economical contexts. To study this point it is necessary to try to evaluate it by identifying the parameters that mainly influence this quality and trying to define reproducible study methodologies in order to compare the different artefacts. Then, another important point is to study the semi-product diffusion and exchange on more or less long distances. To this purpose, crucial chemical data can be found in the slag inclusions (SI) embedded in the metallic artefact, that offers the possibility to identify homogeneous or heterogeneous corpuses but also, in specific cases, to enlighten the production region of the artefacts.

Our research for 10 years concerns an important number of sites and artefacts covering periods from the 1st iron age to medieval times. Following the methodology of former works made in east of France² and in the Swiss Jura³, in the frame of several PhD works⁴, we significantly completed our

1) BERRANGER-FLUZIN 2011.

2) LEROY 1997, LEROY et Al. 1999, FLUZIN et Al. 2000.

3) SERNEELS 1993; ESCHENLOHR 2001; ESCHENLOHR et Al. 2007; SENN-BISCHOFBERGER 2005.

4) ORENGO 2003; BAUVAIS, 2007; PAGES 2008; PAGES 2010; DESAULTY 2008; BERRANGER 2009; LEROY 2010.

pluridisciplinary and diachronic investigations on the French territory for the following areas: Grande Limagne d'Auvergne, Nord du Bassin parisien, Narbonnaise (Languedoc-Roussillon, Provence-Alpes-Côte-d'Azur), Normandy, Pays de Bray, Pyrénées ariégeoises and an important part of central Burgundy. More than 600 ironmaking sites, tens of historical buildings and several hundred artefacts were studied.

These works allowed us to precisely define the internal characteristics of the materials in order to evaluate on the one hand the real nature of the forging activities on given sites, on the other hand the qualitative criteria that could help to identify some specificities and follow exchanges and technical breaks.

Reading wastes on the archaeological sites

Working sequences in bloomery process, as far as post reduction is concerned, are more or less numerous and complex. The post reduction work can begin in the continuity of the smelting stage (compacting of the raw bloom) and strive towards final forming of the artefacts, including the semi-product stage. The *chaîne opératoire* can thus be divided in space and time⁵ and present different stages corresponding to several qualitative nuances of the material.

Depending on periods and geographic areas, the technical system reflects a global organisation more or less sophisticated and structured, varying with the context (rural, urban, etc) and different interactive variables. These variables can be environmental (raw material resources), social (hierarchy, economy, circulation, exchanges, intensity of production ...) and are linked with the nature of the production (skills, specialisation, ...).

Even if, the physico-chemical and thermomechanical characteristics of the material transformation are, up to now, better understood by rigorously crossing analytical methods and observation scales⁶, the restitution of the practice reality from archaeology, ethnoarchaeology and experimentations remains difficult and needs numerous methodological precautions.

Thus, to try to decipher and understand the activity of a given archaeological site, but also the characteristics of the ferrous materials that circulate, it is necessary in a first step, to proceed to an exhaustive study of the vestiges. These vestiges include blooms, metal pieces, fragments of crude metal, slag type (taped, cake, shapeless, ...), slag proportion, lining, semi-products, worked metal fragment, forging scales, rejected fragments, artefacts, tools, etc. These studies must be performed on a significant number of archaeological sites trying to favour the most important corpuses (here archaeological studies of 600 sites, 105 of them archeometrically studied i.e. 700 samples⁷).

Moreover, considering the heterogeneity caused by the smelting and forging at solid state, if the morphological criteria can let to a first typological classification, this aspect is not intrinsically a sufficiently discriminating factor (particularly for quality distinction). Our works shows that there is not a systematic link between morphology and internal characteristics of wastes. This observation is true for both forging slag cakes and manufactured products.

A similarity of shape and aspect is not necessary linked to a same texture, structure or chemical composition. Thus, exclusive morphological approaches must be considered very carefully all the more since a same artefact can present a strong variability inside his matter (compositional or inclusionary cleanliness gradients for metal, more or less stratifications for slag cakes, ...). For this reason, it is necessary to proceed to observation and study of the complete transverse section of artefacts whatever their nature or sizes are.

Toward an evaluation of the metal quality: different ferrous metals

The detailed protocol of metallic semi product analyse will not be presented here and can be found in literature⁸. It consists in classical metallographic preparation with adapted etching: nital

5) PETREQUIN et Al. 2000; FLUZIN 1999 and 2004; FLUZIN et Al. 2004; MANGIN-FLUZIN 2008; BAUVAIS-FLUZIN 2009.

6) MANGIN et Al. 2000; FLUZIN et Al. 2000.

7) FLUZIN et Al. 2011.

8) FLUZIN 1983; FLUZIN et Al. 2000; FLUZIN et Al. 2004.

Type	% of the surface > 0.2w% C	Weighted carbon content
Ferritic	0 - 20	< 0.3
Heterogeneous	20 - 40	0.3 – 0.6
Composite steel	40 – 70	0.6 – 0.8
Steel	70 - 100	> 0.6

Fig. 1: Categories of ferrous alloys with carbon (PAGES 2010, p. 197).

and Oberhoffer reagent. A very important point is to take into account different observation scales from the macroscopic to the microscopic one. If possible, the best way is to make a cross section on the entire artefact to evaluate the different heterogeneities. If that is not possible, representative sampling should be performed at different places of the artefact.

Several parameters will influence the mechanical behaviour of ancient ferrous metals. The first one is of course the carbon content that will change hardness, elastic limit, etc. Nevertheless, as far as ancient artefacts are concerned it is necessary to take into account the eventual presence of phosphorus in the metal but also the one of slag inclusions and porosities. Lastly, it is also important to evaluate if the artefact is made by welding of different metal pieces and to evaluate the quality of the welding lines.

Contrary to contemporary steels, carbon is rarely homogeneously distributed in the metal. Indeed, in most of cases, depending on the local thermodynamic conditions in the furnace, the metal is more or less carburised. Even in the case of relatively carburised materials, the carbon content is heterogeneous.

For this reason, it is difficult to assess correctly the carbon content of a semi-product. To this purpose, a new metallographic approach was proposed to evaluate the iron qualities true two parameters⁹:

- a macroscopic observation under binocular after nital etching on the metallographic cross section for evaluate the proportion of the surface that present carbon content higher that 0.2w%.

- a microscopic observation under microscope which allows to define the surface proportion of different carbon classes was determined as follows: <0.02, 0.02-0.2, 0.2-0.4, 0.4-0.6, 0.6-0.8, 0.8-1, etc. A simple average measurement of the carbon content does not express the distribution of this element accurately. Therefore, we decided to define a weighted carbon content as follows:

$$\%C^* = \sum_{i=1}^n p_i \times x_i$$

where %C* is the weighted carbon content, xi is the mean C content for a given class and pi is the surface proportion corresponding to the given class (sum of pi = 1).

Only these two parameters are able (fig. 1) to completely describe the carburisation degree of an artefact. Then considering it, artefacts can be classified into different categories: ferritic iron, heterogeneous metal made of a mix of iron and steel, composite steel, steel indicates the definition of these categories¹⁰.

As said before, phosphorus is an element that must be taken into account. Several studies clearly demonstrate that the presence in the metal of relatively low quantities of phosphorus (more than 0.1%) can drastically change the mechanical behaviour of it and consequently his commercial or technical value. Moreover it seems that specific technical gestures must be used to manage to forge and weld it correctly¹¹. Thus, it appears that phosphorus iron must be considered as a specific material. Moreover, it will be important in the future to try to evaluate the real place of this material in the technical landscape of each period. For this reason, any study about semi-finished products must evaluate on the one hand the amount of phosphorus present in the materials and, in the other hand its distribution. Specific ghost structures after nital etching appears

9) PAGES 2010; PAGES et. Al. 2011-a; PAGES et. Al. 2011-b.

11) VEGA et Al. 2002: VEGA et Al. 2003.

10) PAGES 2010; PAGES et. Al. 2011-a; PAGES et. Al. 2011-b.

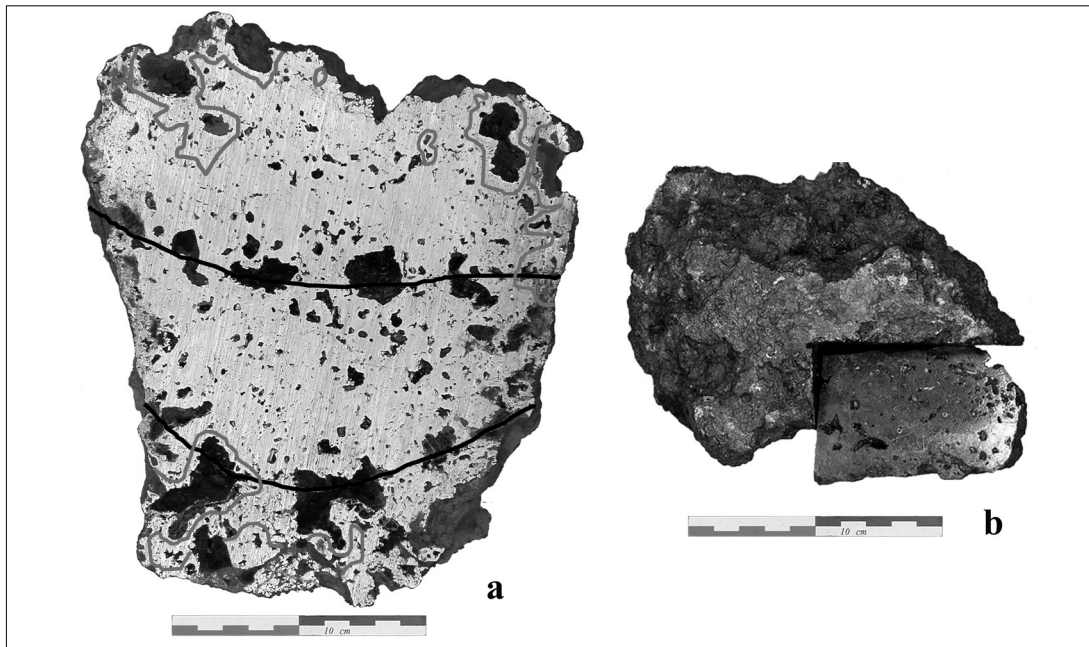


Fig. 2: a) Raw bloom from Piani d'Erna (Italy), 2nd century BC-1st century AD; weight 33 and 38 kg (FLUZIN 2006). b) Bloom from Selongey (Burgundy, France), Gallo-Roman, weight 2.37 kg.

on polished surfaces for P contents between 0.1 and 0.6 mass%. They can also be easily detected after an Oberhoffer etching. For higher contents, an Energy Dispersive Spectrometry coupled to a Scanning Electron Microscope analyse on the metallic matrix can indicate the presence of this element.

Depending on the smithing stage (cleansing), on the slag quantity initially present in the raw bloom, but also on the final shape of the artefact, more or less slag inclusions remain embedded in the semi and final products. We will show that they are a very useful mean to distinguish smelting processes and provenances¹². However, as far as the mechanical behaviour of the metal is concerned, they can modify drastically the quality of the metal. Moreover, it is completely impossible to estimate *ab initio* the mechanical behaviour of a given artefact if it contains numerous inclusions. This effect was observed by performing uniaxial tensile tests on samples taken in bars reinforcing the Vincennes castle dungeon in France (XVIth c.)¹³. Different samples taken in bars presenting the same morphology, the same heterogeneous structure made of mixed carbon and steel and containing numerous slag inclusions have a completely different behaviour. This is also the case for samples taken in the same bar at different locations. Thus, to estimate the quality of the semi-finished product it is of great importance to evaluate the surface proportion of the slag inclusions but also porosities. It is then possible to express the cleanliness of the semi product.

Lastly, to evaluate the quality of an artefact or a semi product it is necessary to detect the welding lines and their quality but also the eventual voluntary thermo mechanical treatments (carburizing, quenching, tempering, etc). Practically, different operations must be distinguished: simple welding by hammering of porous or heterogeneous material, welding after folding and hammering, welding together separate metal pieces. Moreover, the most significant parameter to consider is the textural and structural homogeneity.

It appears after this short review that the quality of a ferrous semi-product is a very complex thing to evaluate. First, it is linked to the convolution of numerous parameters from the carbon content to the slag inclusion number and distribution. A first approach, after quantifying all these

12) DILLMANN-L'HERITIER 2007.

13) DILLMANN 2007; DILLMANN et Al. 2003; L'HERITIER et Al. 2005.

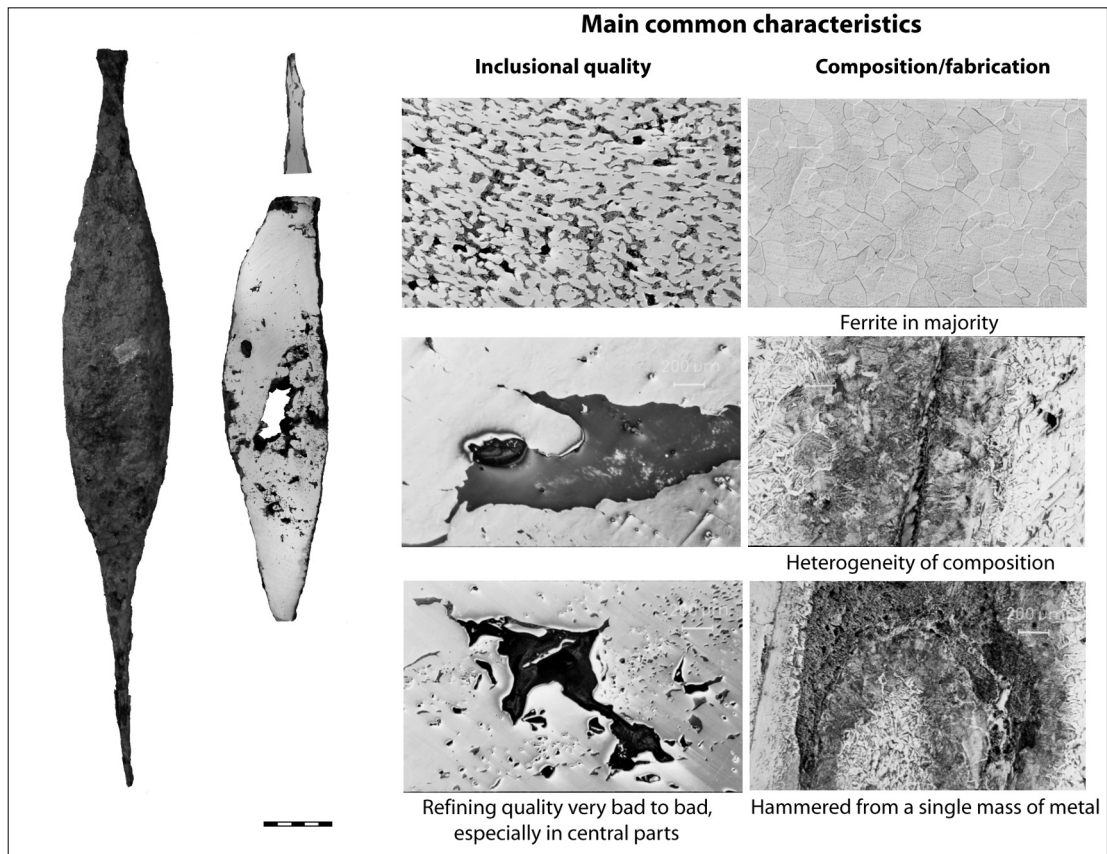


Fig. 3: Iron bipyramidal bar from Nottonville (Eure et Loir, France), 8th-5th century BC (¹⁴C datation). Weight 4,9 kg (BERRANGER 2009).

parameters is to underline the ones that will have the main influence on the mechanical behaviour: a carburised steel without slag inclusion is completely different from a ferritic iron full of impurities. Nevertheless it is not so easy to make a difference between the numerous heterogeneous materials that are found in the archaeological sites: what about the comparison between a composite steel containing slag inclusions and a phosphoric iron? These points will be investigated in the future. Secondly, the notion of quality is, of course, relative and depends on the technico-economical context but also on the final use of the metal. At this stage, a necessary confrontation with the archaeological and historical data is necessary.

From raw metal to semi-products: examples of results

Nevertheless, considering all the information gathered in the metal, some interpretations of archaeological sites but also a global view of production and exchanges in given areas can be proposed from the study of semi-products. Following the sequences of the *chaîne opératoire*, several examples are given.

Because of their rarity in archaeological context, studies on raw blooms are not so numerous (fig. 2). The most of our observations (24 blooms morphologically studied including metallographic studies on 17 blooms or fragment of 2 to 38 kg) confirms the intrinsic compositional heterogeneity of blooms (numerous slag inclusions and porosities, high variability in carbon distribution, from 0.02 to 0.9%C and sometimes presenting locally cast iron structures). This latter material can sometimes be considered as waste but this assertion is not systematic. Moreover, some blooms can be very homogeneous (ferritic or low carburised steel) showing an excellent mastering of the

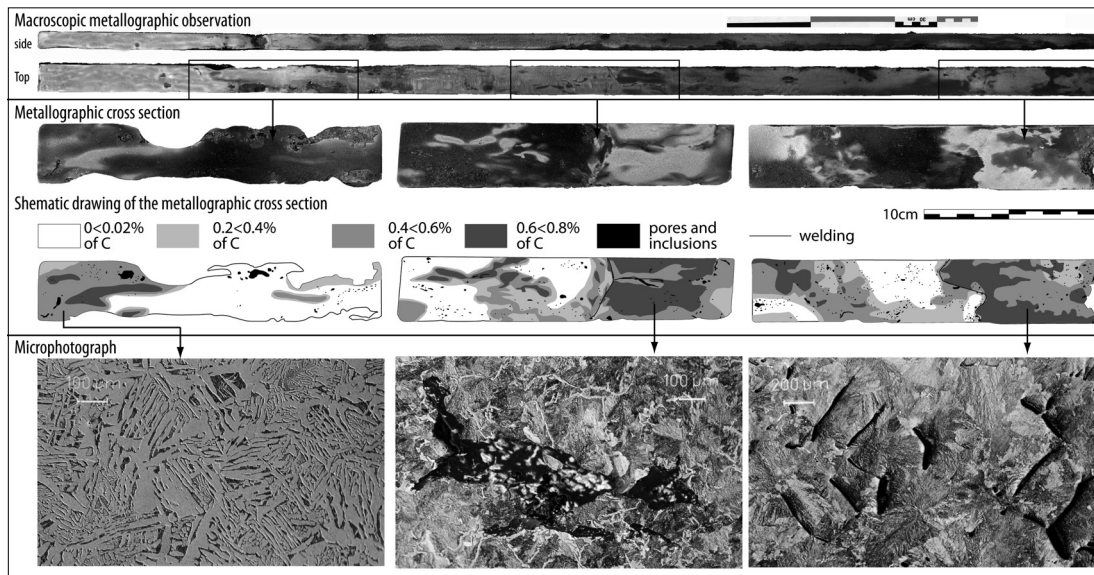


Fig. 4: An example of the metallographic observation of a bar of Saintes-Maries-de-la-Mer (1LSM10_1) at the macroscopic and the microscopic scale after Nital etching (PAGES et Al. 2011).

smelting stage. This kind of artefact is also easily forgeable¹⁴. Their presence in open urban areas and *oppida* shows that the raw materials (blooms) were exchanged as “raw semi product”, probably on small distances and, that these areas unquestionably concentrated supplying and redistributed it¹⁵.

As far as typology and morphology of semi product are concerned¹⁶, it appears that in most of cases that we studied (730 artefact archaeologically examined including about 200 archaeometric studies), bipyramidal or salmon type ingots (more than 80 artefacts analysed, fig. 3) corresponds to a bloom or a bloom fragment very summarily compacted (sometimes folded down). We also confirm the hypothesis that the more or less strong elongation at their extremity was made in order to demonstrate the forgeability of the metal (qualitative test). In a general way, the thinner the semi product, the higher the cleanliness (compacting rate, and forming work).

It is important to mention the exception of the bars from the “Saintes-Maries-de-la-Mer”, dated from 1c. AD (Eleven roman ships. Every ship contains between 20 to 150 tons of ferrous bars¹⁷). Indeed, despite of their significant weights (between 1.5 to 33 kg) and their crosssections that can attempt 10x4 cm², the complete archaeometric study (54 bars) reveals a high inclusion cleanliness with a certain technological and morphological normalisation (fig. 4). Moreover, the longer bars (1.5 m) are made of 2 to 4 blooms welded together by a high quality work. These welding lines can be considered as true technological feats.

To sum up these results. Metallographic analyses show the semi-product morphology of the bars is correlated to the metal quality. It means that the standard seems to be linked to the metal quality: each specific morphology is linked to a particular metal. This association is not linked to the ship loading. It can be observed in all the studied ships.

At least six different reducing systems categories can be distinguished¹⁸:

- Category 1: High MnO contents.
- Category 2: High P₂O₅ content.
- Category 3: Higher MgO/Al₂O₃ ratios without significant MnO or P₂O₅ levels.

14) FLUZIN 2006.

17) PAGES et Al. 2008, 2011; PAGES 2008 and 2010.

15) BAUVAIS 2007; BERRANGER 2009.

18) PAGES et Al. 2008, 2011-a and 2011-b.

16) PLEINER et Al. 2003; PLEINER 2006.

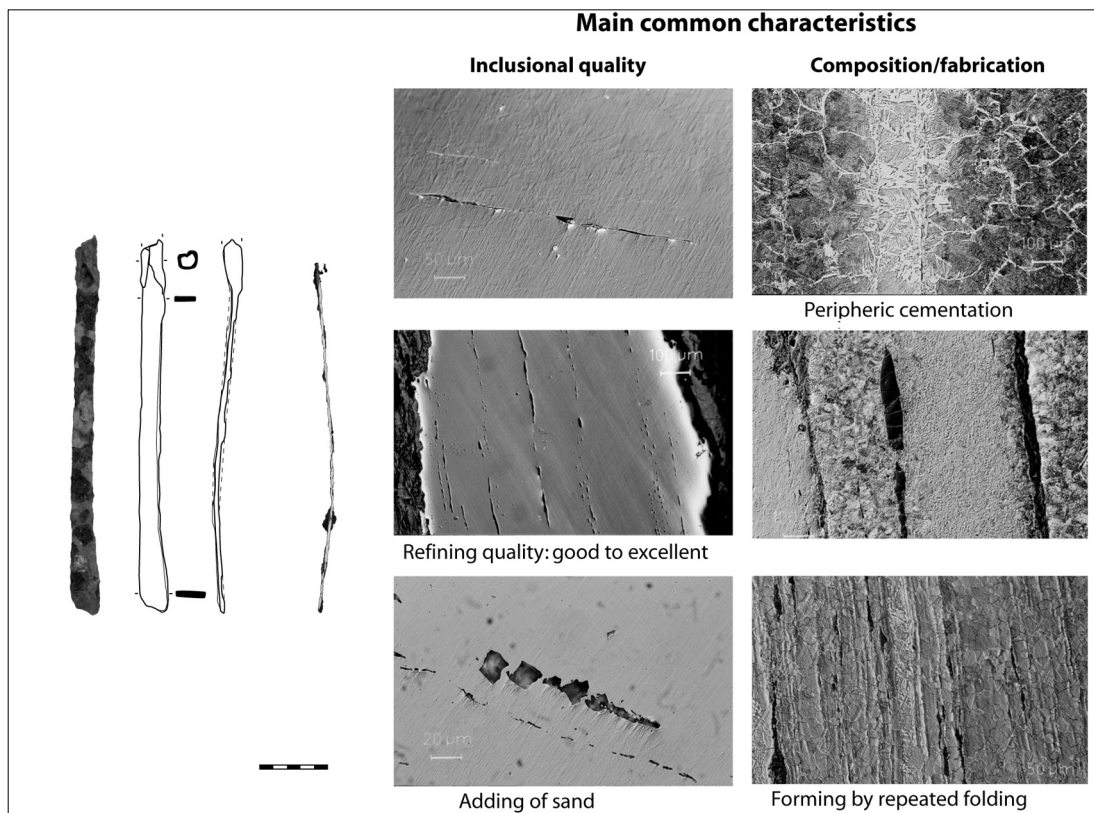


Fig. 5: Iron “socket bar” coming from St. Maur (Picardie, France), 2nd century BC. Weight 69 g (BERRANGER 2009).

- Category 4: Lower Al₂O₃/SiO₂ ratios without significant MnO or P₂O₅ levels.
- Category 5: Higher K₂O/CaO without significant MnO or P₂O₅ levels.
- Category 6: no particular composition.

The fact that some bars are constituted of blooms with different major chemical element signature could indicate that semi-products are not systematically forged on the reduction site as it is often asserted for this period. They could also be realised in different workshops more or less away from the reduction workshop and that import products from different workshops to manufacture the bars.

Another form of trade iron are “Currency bars”¹⁹. They present, mainly, a good to excellent quality of refining (depending of the heterogeneity of the initial bloom), and are constituted by a single bloom, sometimes hammered by repeated folding (more than 75 objects were examined by our team).

A new type of semi-product (300 specimens already studied), with the same morphology as the currency bars, but with a lower mass, was also evidenced: socket bars (fig. 5). They are small flat iron pieces with a socket (about 400x20x3 mm, average weight: about 100 g). These products seem to be mainly located in the French *Bassin Parisien* during the Iron Age²⁰. Their studies reveal some qualitative particularities:

- Excellent inclusion cleanliness
- Intense hammering by successive folding that could conduct to very good mechanical properties
- Quasi-systematic cementation treatment. This cementation was probably made in order to facilitate welding by lowering the weld ability temperature.

19) CREW 1994.

20) BAUVAIS 2007; BAUVAIS-FLUZIN 2007; BERRANGER et Al. 2007; BERRANGER 2009; BERRANGER-FLUZIN 2011.

Considering these aspects, it seems that these latter semi-products show specific qualities indicating an elaborated functional role.

The chemical analysis of slag-inclusions contained in 19 socket-bars from 8 different sites of this sector permitted a more precise understanding of their circulation. The socket-bars, of local manufacturing and of local using, are composed of metals from various origins. This remark tends to confirm the massive importation of crude iron from distant sectors and a local transformation²¹.

Conclusion

The aim of this paper was to present a review of the methodological aspect of our team for several years. In order to understand the production contexts of semi-products (technological, economical, historical), a pluridisciplinary approach has been attempted, from the understanding of the archaeological site to the one of the materials. Combining all sorts of information, gathered on wastes and products at different periods and on different areas, all these aspects can be enlightened.

Philippe Fluzin
Marion Berranger
Sylvain Bauvais
Gaspard Pagès
Philippe Dillmann
LMC IRAMAT UMR5060 CNRS
F-90000 Belfort
philippe.fluzin@utbm.fr

Riassunto

Un approccio archeologico e archeometrico dei semilavorati di ferro: tipologia, qualità e circolazione. In questo articolo viene presentato l'aspetto metodologico del lavoro multidisciplinare che il nostro gruppo conduce sui semilavorati. Esso combina le ricerche sugli scarti e sui prodotti, tenendo presente la stretta relazione che vi è tra l'archeologia e l'archeometria. In aggiunta all'analisi morfologia e tipologica esterna, vengono condotte sui manufatti differenti osservazioni metallografiche e analisi fisico-chimiche (particolarmente sugli inclusi nelle scorie) per ottenere una migliore comprensione dell'organizzazione dei siti e dell'economia tecnica in diverse aree durante determinati periodi.

References

- BAUVAIS S.
2007 *Evolution de l'organisation des activités de post-réduction dans le Nord du Bassin Parisien au 2nd Age du fer: études multidisciplinaires de la chaîne opératoire en métallurgie du fer*, PhD Thesis, Belfort, Université de Technologie de Belfort Montbéliard.
- BAUVAIS S.-FLUZIN P.
2007 *Réflexion sur l'organisation technico-sociale des activités de forge à La Tène finale dans l'Aisne* (02), *Revue d'Archéométrie*, 30, pp. 25-43.
- 2009 *Archaeological and Archeometrical Approaches of the Chaîne Opératoire in Iron and Steel making: Methodology for a Regional Evolution Study*, in V. ROUX-S. ROSEN (dir.), *Techniques and People: anthropological perspectives on technology in the archaeology of the proto-historic and early historic periods in the Southern Levant*, Workshop of the CRFJ, Jerusalem, Paris, pp. 157-178.
- BERRANGER M.
2009 *Le fer, entre matière première et moyen d'échange, en France du VIIe au Ier s. av. J.-C. Approches interdisciplinaires*, PhD thesis, Université Paris 1, Panthéon-Sorbonne.
- BERRANGER M.-BAUVAIS S.-FLUZIN P.
2007 *Socket bars: multidisciplinary results (archaeology and archaeometry) on a specific iron semi-product in north of France*, in METALLURGIA, A.I.D. (Ed.) *Archaeometallurgy 2007*, Aquileia.

21) BERRANGER et al. 2007.

- BERRANGER M.-FLUZIN P.
 2009 *Le village celtique de Levroux: nature et organisation des activités sidérurgiques*, in O. BUCHSENSCHUTZ-M.-B. CHARDENOUX-S. KRAUSZ-M. VAGINAY, *L'Âge du Fer dans la boucle de la Loire. Les Gaulois sont dans la ville*, Actes du XXXII^e colloque de l'Association Française pour l'Étude de l'Âge du Fer (Bourges 1-4 mai 2008), 35^e suppl. à la Revue Archéologique du Centre de la France, pp. 19-37.
- 2011 *From raw iron to semi-product: quality and circulation of materials during the iron age in France*, *Archaeometry*.
- COUSTURES M.-P.-BÉZIAT D.-TOLLON F.
 2003 *The use of trace element analysis of entrapped slag inclusions to establish ore-bar iron links: examples from two gallo-roman iron-making sites in France (Les Martyrs, Montagne Noire, and Les Ferrys, Loiret)*, in *Archaeometry*, 45, pp. 599-613.
- CREW P.-CREW S.
 1994 *The experimental production of bar iron*, in M. MANGIN (ed.) *La sidérurgie ancienne de l'Est de la France dans son contexte européen. Archéologie et archéométrie*, Besançon, Les Belles Lettres.
- DESAULTY A.-M.
 2008 *Apport des analyses chimiques multi technique à la compréhension du comportement des éléments traces dans les filières sidérurgiques anciennes. application aux études de provenance et à la distinction des procédés. Le cas du Pays de Bray Normand*, PhD Thesis Belfort, Université de Technologie de Belfort Montbéliard.
- DESAULTY A.-M.-DILLMANN P.-L'HERITIER M.-MARIET C.-GRATUZE B.-JORON J.-L.-FLUZIN P.
 2009 *Does it come from the Pays de Bray? Examination of an origin hypothesis for the ferrous reinforcements used in French medieval churches using major and trace element analyses*, in *Journal of Archaeological Science*, 85, pp. 2445-2462.
- DESAULTY A.-M.-MARIET C.-DILLMANN P.-JORON J.-L.-FLUZIN P.
 2008 *The study of provenance of iron objects by ICP-MS multi-elemental analysis*, *Spectrochimica Acta Part B*.
- DESAULTY A.-M. MARIET C.-DILLMANN P.-JORON J.-L.-GRATUZE B.-CARLIER C.M.-L.-FLUZIN P.
 2007 *Trace elements behaviour in direct- and indirect-iron metallurgy: the case of Pays de Bray (France)*, *Archaeometallurgy 2007*, Aquileia.
- DILLMANN P.
 2007 *Les métaux ferreux dans les monuments historiques avant le XIX^e siècle, structure et propriétés des matériaux*, in *Monumental*, 2, pp. 92-97.
- DILLMANN P.-ARANDA R.-LHERITHIER M.-FLUZIN P.
 2005 *Forging of iron-steel artifacts: archaeology, experiments and archaeometry*, in *Iron, History and Heritage*, 1st International Conference of Paleosiderurgy and Industrial Heritage Recovery, INASMET, San Sebastian.
- DILLMANN P.-BERNARDI P.-FLUZIN P.
 2003 *Use of iron for the building of medieval monuments. The Palais des Papes in Avignon and other French buildings*, *Archaeometallurgy in Europe*, AIM, Milan.
- DILLMANN P.-L'HERITIER M.
 2007 *Slag inclusion analyses for studying ferrous alloys employed in French medieval buildings: supply of materials and diffusion of smelting processes*, in *Journal of Archaeological Science*, 34, pp. 1810-1823.
- DILLMANN P.-TEREYGEOL F.-VERNA C.
 2006 *Premières analyses métallographiques des produits sidérurgiques trouvés sur le site médiéval de Castel-Minier (Aulus-les-Bains, 09)*, in *La Revue d'Archéométrie*, 29, pp. 7-14.
- ESCHENLOHR L.
 2001 *Recherches archéologiques sur le district sidérurgique du Jura central suisse*, Lausanne.
- ESCHENLOHR L.-FRIEDLI V.-ROBERT CHARRUE LINDER C.-SENN M.
 2007 *Develier courtételle, un habitat rural mérovingien. Métallurgie du fer et mobilier métallique*, Office de la culture et Société jurassienne d'Emulation, Porrentruy.
- FLUZIN P.
 1983 *Notions élémentaires de sidérurgie*, in N. ECHARD (ed.), *Métallurgies africaines. Nouvelles contributions*, Musée de l'Homme, Paris.
- 1999 *Il processo siderurgico; evoluzione storica e indizi archeometrici*, and *Ponte di val Gabbia III*, and *I reperti metallici della forgia. Primi risultati dello studio metallografico*, in CUCINI TIZZONI C.-TIZZONI M. (a c. di), *La miniera perduta. Cinque anni di ricerche archeometallurgiche nel territorio di Bienno, Breno*, pp. 61-92 e 189-194.
- 2004 *The process chain in iron and steel making: archaeological materials and procedures. The contribution of metallographical studies*, in H. BOCOUM (ed.), *The origins of iron metallurgy in Africa. New lights on its antiquity, west central Africa*, Editions UNESCO, pp. 65-96.
- 2006 *Premiers résultats des études métallographiques concernant les masses de métal brutes*, in M. TIZZONI-C. CUCINI-M. RUFFA (a c. di), *Alle origini della siderurgia lecchese. Ricerche archeometallurgiche ai Piani d'Erna*, Materiali, Lecco, pp. 129-146.
- FLUZIN P.-BAUVAIS S.-BERRANGER M.-PAGES G.-DILLMANN P.
 2011 *The multidisciplinary approach (archaeology and archaeometry) to bloomsmithing activities in France: examples of results from the last twenty years*, in J. HOŠEK-H. CLEERE-L. MIHOK (pub.), *The archaeometallurgy of Iron. Recent Developments in Archaeological and Scientific Research*, The Institute of Archaeology of the ASCR, Prague.
- FLUZIN P.-PLOQUIN A.-DABOSI F.
 2004 *Approches métallurgiques et archéométriques*, in M. MANGIN (ed.), *Le Fer*, Errance, Paris.

- FLUZIN P.-PLOQUIN A.-SERNEELS V.
2000 *Archéométrie des déchets de production sidérurgique. Moyens et méthodes d'identification des différents éléments de la chaîne opératoire directe*, in Gallia, 57, pp. 1-158.
- L'HÉRITIER M.
2007 *L'utilisation du fer dans l'architecture gothique. Les cas de Troyes et de Rouen*, 5 voll., 1300 pp., PhD thesis, Université Paris 1, Panthéon, Sorbonne.
- L'HÉRITIER M.-JUHIN A.-DILLMANN P.-ARANDA R.-BENOIT P.
2005 *Utilisation des alliages ferreux dans la construction monumentale du Moyen Âge. État des lieux de l'avancée des études métallographiques et archéométriques*, La Revue d'Archéométrie, 29, pp.117-132.
- LEROY M.
1997 *La sidérurgie ancienne en Lorraine avant le haut-fourneau. Etude du développement historique et des conditions techniques de l'utilisation du minerai oolithique lorrain (la minette) en métallurgie de réduction directe*, CNRS, Paris.
- LEROY S.
2010 *Circulation au Moyen Âge des matériaux ferreux issus des Pyrénées ariégeoises et de la Lombardie. Apport du couplage des analyses en éléments traces et multivariées*, PhD Thesis, Belfort, Université de Technologie de Belfort Montbéliard.
- LEROY S.-DESAULTY A.-M.-DILLMANN P.-TEREYGEOL F.-VERNA C.-BERTRAND L.
2007 *First examinations of ore, slag and iron artefacts from the iron-making site of Castel-Minier (Aulus-les-Bains, 09 France)*, Archaeometallurgy, Aquileia.
- LEROY M.-MERLUZZO P.-FLUZIN P.-LECLERE D.-AUBERT M.-PLOQUIN A.
1999 *La restitution des savoir-faire pour comprendre un procédé technique: l'apport de l'expérimentation en archéologie du fer*, in P. PETREQUIN-P. FLUZIN-J. THIRIOT-P. BENOIT (eds.), *Arts du feu et productions artisanales*, XXe Rencontres Internationales d'Archéologie et d'Histoire d'Antibes, APDCA, Antibes.
- MANGIN M.-FLUZIN P.
2008 *La sidérurgie dans l'est des Gaules de La Tène au Haut Moyen Âge. Bilan des recherches et perspectives*, in M. MOLIN (dir.), *Archéologie et histoire des techniques du monde romain*, De Boccard, Paris, pp. 43-62, 18 figg.
- MANGIN M.-FLUZIN P.-COURTADON J.-L.-FONTAINE M.-J.
2000 *Forgerons et paysans des campagnes d'Alésia (Haut-Auxois, Côte-d'Or) Ier siècle avant- VIIIe siècle après J.C.*, CNRS Edition, Paris.
- ORENGO L.
2003 *Forges et forgerons dans les habitats laténiens de la Grande Limagne d'Auvergne: fabrication et consommation de produits manufacturés en fer en Gaule à l'Âge du fer*, Editions Monique Mergoïl, Montagnac.
- PAGÈS G.
2008 *La métallurgie du fer en France méditerranéenne de l'Antiquité au début du Moyen Âge: jalons d'une approche interdisciplinaire*, PhD thesis, Université de Montpellier.
- 2010 *Artisanat et économie du fer en France méditerranéenne de l'Antiquité au début du Moyen Âge: une approche interdisciplinaire*, Monographies Instrumentum, 37, Monique Mergoïl ed., Montagnac, 316 pp.
- PAGÈS G.-DILLMANN P.-FLUZIN P.-LONG L.
2011 *A study of the roman half-products of Saintes-Maries-de-la-Mer (Bouches-du-Rhône, France). A proposal for a comprehensive metallographic approach*, Journal of Archaeological Science, 38/6, pp. 1234-1252.
- PAGÈS G.-FLUZIN P.-LONG L.
2011 *L'acier, une variété de fer parmi d'autres? Approches méthodologiques des demi-produits des épaves romaines des Saintes-Maries-de-la-Mer (Bouches-du-Rhône, France)*, in P. DILLMANN-L. PÉREZ-C. VERNA (dir.), *L'acier en Europe avant Bessemer*, Actes du colloque international (Paris 2005), Collection Méridiennes, Série Histoire et Techniques, CNRS/Université de Toulouse-Le Mirail, Toulouse, pp. 147-174.
- PAGÈS G.-LONG L.-FLUZIN P.-DILLMANN P.
2008 *Réseaux de production et standards de commercialisation du fer antique en Méditerranée: les demi-produits des épaves romaines des Saintes-Maries-de-la-Mer (Bouches-du-Rhône, France)*, Revue Archéologique de Narbonnaise, 41, pp. 261-283.
- PETREQUIN P.-FLUZIN P.-THIRIOT J.-BENOIT P.
2000 (eds.) *Arts du feu et productions artisanales*, XXe Rencontres Internationales d'archéologie et d'histoire d'Antibes, APDCA, Antibes.
- PLEINER R.
2006 *Iron in Archaeology. Early European Blacksmiths*, Archeologický ústav AV ÈR, Prague.
- PLEINER R.-FLUZIN P.-MANGIN M.-VEGA E.-DILLMANN P.-BILLON M.-RABEISEN E.
2004 *Lingots et couteaux en fer d'Alésia: études archéométriques*, in Revue archéologique de l'Est, 52, 2003, pp. 91-130.
- SENN-BISCHOFBERGER M.
2005 *Das Schmiedehandwerk im nordalpinen Raum von der Eisenzeit bis ins frühe Mittelalter. Rahden/Westf., Leidorf.*
- SERNEELS V.
1993 *Archéométrie des scories de fer. Recherches sur la sidérurgie ancienne en Suisse occidentale*, Lausanne.
- STEWART J.W.-CHARLES J.A.-WALLACH E.R.
2001 *Iron-Phosphorus-Carbon system part I. Mechanical properties of low carbon iron-phosphorus alloys*, in Materials science and technology, 16, pp. 275-282.
- VEGA E.-DILLMANN P.-FLUZIN P.
2002 *Contribution à l'étude du fer phosphoreux en sidérurgie ancienne*, in La Revue d'Archéométrie, 26, pp. 197-208.
- VEGA E.-DILLMANN P.-L'HÉRITIER M.-FLUZIN P.-CREW P.-BENOIT P.
2003 *Forging of phosphoric iron. An analytical and experimental approach*, in Archaeometallurgy in Europe, AIM, Milan.